

# Optical trapping and optical force positioning of two-dimensional materials

M. G. Donato,<sup>\*a</sup> E. Messina,<sup>a‡</sup> A. Foti,<sup>a</sup> T. Smart,<sup>b</sup> P. H. Jones,<sup>b</sup> M. A. Iatì,<sup>a</sup> R. Saija,<sup>c</sup> P. G. Gucciardi,<sup>a</sup> and O. M. Maragò<sup>\*a</sup>

In recent years, considerable effort has been devoted to the synthesis and characterization of two-dimensional materials. Liquid phase exfoliation (LPE) represents a simple, large-scale method to exfoliate layered materials down to mono- and few-layer flakes. In this context, the contactless trapping, characterization, and manipulation of individual nanosheets hold perspectives for increased accuracy in flake metrology and assembly of novel functional materials. Here, we use optical forces for high-resolution structural characterization and precise mechanical positioning of nanosheets of hexagonal boron nitride, molybdenum disulfide, and tungsten disulfide obtained by LPE. Weakly optically absorbing nanosheets of boron nitride are trapped in optical tweezers. Analysis of the thermal fluctuations allows a direct measurement of optical forces and the mean flake size in liquid environment. Measured optical trapping constants are compared with T-matrix light scattering calculations to show a quadratic size scaling for small size, as expected for a bidimensional system. In contrast, strongly absorbing nanosheets of molybdenum disulfide and tungsten disulfide are not stably trapped due to the dominance of radiation pressure over the optical trapping force. Thus, optical forces are used to pattern a substrate by selectively depositing nanosheets in short times (minutes) and without any preparation of the surface. This study will be useful for improving ink-jet printing and for a better engineering of optoelectronic devices based on two-dimensional materials.

## 1 Introduction

Two-dimensional, layered materials<sup>6</sup> form a large family of crystals having a multi-layer structure with strong in-plane covalent bonds between atoms and much weaker Van der Waals interaction between layers. Graphene remains the prototypical structure for such materials<sup>44</sup>, but many other compounds, among which are hexagonal boron nitride (hBN), the transition metal dichalcogenides (TMDs, with the stoichiometry  $\text{MX}_2$ , M being a transition metal and X a chalcogen atom) and the transition metal oxides (TMOs), are actively studied for methods of synthesis<sup>13,42,57</sup>, and for the characterization<sup>3,20,22,26,28</sup> and applications<sup>6,36,43,63</sup> of these exciting materials. The synthesis method-of-choice depends largely on the best compromise between price and material quality with regard to the particular application. Liquid phase exfoliation<sup>42</sup> (LPE) has been already proved as a simple, large-scale method to exfoliate graphite<sup>23</sup> and other layered materials<sup>13,57</sup> down to mono- and few-layer flakes. The relative ease of production of these 2D atomic crystals via this method is a result of the asymmetry of the binding forces inside and between the layers.

Hexagonal boron nitride has a layered structure that on exfoliation produces nanosheets very similar to graphene, in which each C-C pair is replaced by a B-N couple with a bond length of 1.44 Å<sup>29</sup>. Due to these analogies, several studies<sup>29</sup> are in progress regarding the possibility of replacing graphene with hBN when its stronger thermal stability is required. Moreover, hBN is also one of the best electrically insulating thermal conductors, so its sheets have the potential for use as dielectric substrates for graphene and other layered materials in optoelectronic applications. It has been also reported that it can be used as a protective barrier for metals and as reusable substrates of Au particles for applications such as surface-enhanced Raman spectroscopy (SERS)<sup>30</sup>. Moreover, hBN is more than a simple dielectric: it is naturally hyperbolic, which could pave the way to its application in the hot field of metamaterials, where several interesting exotic effects have been observed<sup>49</sup>.

Molybdenum disulfide ( $\text{MoS}_2$ ) and tungsten disulfide ( $\text{WS}_2$ ) belong to the family of TMDs and, as such, their two dimensional version consist of a three-layered structure in which each layer of metal atoms (Mo or W) is sandwiched between two layers of sulphur atoms<sup>65</sup>. The physical property that drives the research on these materials is their energy bandgap, that is essential for the realization of thin electronic devices. Moreover, the bandgap switches from indirect to direct when the number of layers is reduced to one, which is particularly appealing for photonics<sup>10</sup>, optoelectronics<sup>65</sup> and energy storage<sup>6</sup> applications. A further interesting application is the realization of Van der Waals heterostructures<sup>18</sup>, in which 2D layers of different origin can be stack on top of each other. In this regard, crucial assistance could be provided by optical tweezers<sup>2,25</sup>, that have been already proved useful for controlled manipulation of micro- and nano-sized objects<sup>35</sup>.

Optical trapping stems from the conservation of the electromagnetic momentum in the light-matter interaction<sup>25</sup>. The total force

<sup>0a</sup> CNR-IPCF, Istituto per i Processi Chimico-Fisici, V.le F. Stagno D'Alcontres 37, I-98158, Messina, Italy. Fax: 39 090 3974130; Tel: 39 090 39762249; E-mail: donato@ipcf.cnr.it, onofrio.marago@cnr.it

<sup>0b</sup> Department of Physics and Astronomy, University College London, London WC1E 6BT, UK.

<sup>0c</sup> Dipartimento di Scienze Matematiche e Informatiche, Scienze Fisiche e Scienze della Terra, Università di Messina, V.le F. Stagno D'Alcontres 31, I-98166, Messina, Italy.

<sup>0†</sup> Electronic Supplementary Information (ESI) available: Optical characterization of exfoliated samples, Optical trapping and metrology of boron nitride, Calculation of optical forces in the dipole approximation, Optical forces in the T-matrix formalism for non-spherical particles, Raman spectroscopy of pushed  $\text{MoS}_2$  at 785nm, Supplementary Videos. See DOI: 10.1039/b000000x/

<sup>0‡</sup> Current address: CNR-ISMN, Istituto per lo studio dei materiali nanostrutturati, Via Salaria Km 29300, 00015, Monterotondo Stazione, Roma, Italy.

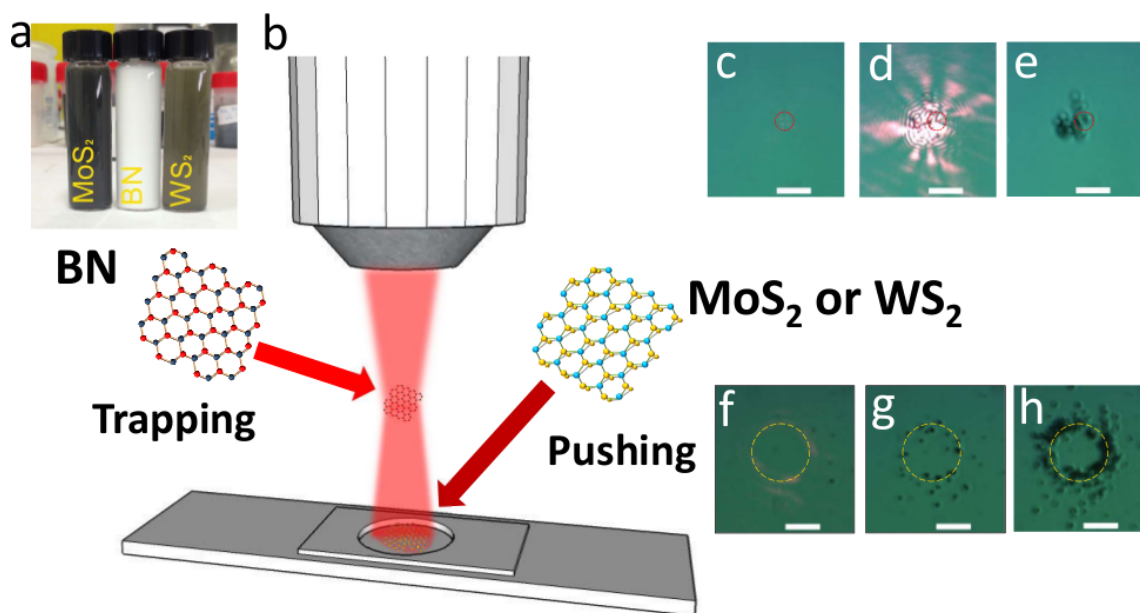


Figure 1: (a) Aqueous dispersions of the 2D materials. (b) Sketch of the experimental setup. A high numerical aperture objective (NA = 1.3) is used to obtain a diffraction limited spot. Particles are trapped in the laser focus when the optical gradient force is greater than the scattering force. Conversely, the particles are optically pushed toward the bottom of the sample cell. If BSA is diluted in the aqueous medium, the particles stick to the walls of the cell and surface patterning is obtained. (c)-(e) Optical microscope images recorded at the beginning of the pushing process of WS<sub>2</sub> with a Gaussian beam (c) and after approximately 90 seconds (d, e). In (d), the scattering of the laser light due to the formation of the WS<sub>2</sub> aggregate is clearly observed. The dashed circles are guides for the eye indicating the location of the beam waist. (f)-(h) Optical microscope images registered at the beginning of the pushing process of MoS<sub>2</sub> (f) with a Laguerre-Gauss beam ( $l = 30$ ), after approximately 2 minutes (g) and after approximately 18 minutes (h). The dashed circles are guides for the eye indicating the location of the high intensity doughnut beam (see also Supplementary Video 3).

acting on a small (*i.e.*, much smaller than the optical wavelength) particle may be separated into the sum of two main contributions<sup>2</sup>: the *gradient force*, which in optical tweezers arises from the strong variation of light intensity when a laser beam is focused by a high numerical aperture objective, and the *scattering force*, proportional to the particle extinction cross section<sup>25</sup>, which tends to push the particle along the beam propagation direction. If the gradient force is stronger than the radiation pressure, the particle is trapped, namely, it is confined close to the beam focus by optical forces alone. The balance between trapping forces and propelling forces is connected to the structural (shape) and optical properties of the particle. In general, optical trapping of nanoparticles is difficult, because the gradient force scales (approximately) as the particle volume, and is easily overwhelmed by thermal fluctuations<sup>35</sup>. Several strategies have been used to enhance the gradient force with respect to repulsive forces, based on increased particle polarizability<sup>11,27,38,60</sup> and hybridization<sup>58,59</sup>, or on particle geometrical anisotropies<sup>24,33,34,41,46,50</sup>, or even on the use of non Gaussian beams, having special polarization states<sup>14,45,67</sup>. However, even when the trapping is unstable, optical forces can still help in manipulation: optical pushing of gold nanoparticles has been used for the all-optical stamping of substrates<sup>21,39,64</sup> and to form aggregates<sup>16</sup> that act as sensors for the high-sensitivity detection of molecular species directly in liquid environment.

In this work, we show that optical tweezers can be used for optical trapping and optical force positioning of two-dimensional nanoparticles obtained by LPE. Combined force and Raman spectroscopy of optically trapped individual hBN nanosheets allows one to get information on the flake size and number of layers directly in liquid environment. Experimental results on optical trapping are compared with T-matrix calculations of optical forces versus flake size, exploring its size scaling. Optical pushing of MoS<sub>2</sub> and WS<sub>2</sub> nanoparticles permits us to pattern simple substrates without the need for complex, costly or special preparation of the surface. We study the dynamics of the deposition by Raman and photoluminescence spectroscopy, excited by the pushing beam, revealing the time evolution of the flake aggregation.

## 2 Results and discussion

### 2.1 Two-dimensional materials

The layered material samples used in this work are obtained by LPE<sup>13,31,57</sup> in aqueous environment (see the Methods section for further details). In brief, the procedure is based on surfactant-assisted ultrasonication of the layered materials-water dispersions, where sodium cholate is used as surfactant to stabilize the flakes, preventing their re-aggregation. We follow the protocols described in Smith et al.<sup>57</sup> that ensures a Z-potential of approximately  $-40$  meV, which is an indicator of very good colloidal stability. Indeed, this is also observed in our samples that appear to be stable, with no visible re-aggregation, after several months. A tuning of surface charge has proved to be important for increase of optical forces on very small nanoparticles<sup>52</sup>. While tuning the Z-potential of layered material dispersions might help stabilizing the optical trapping of flakes below 100 nm size, we expect a change in Z-potential to have a negligible effect on our layered flakes that have a larger average size.

Once sonicated, the dispersions are centrifuged to remove the unexfoliated powder. After centrifugation, the surfactants are extracted and used for spectroscopy, metrology and pushing experiments. Lotya et al.<sup>31</sup> showed that there is a precise relation between the average flake size, as measured from TEM analysis, and centrifugation rate. For our centrifugation rate (1500 rpm) this corresponds to a lateral flake size in the range  $0.1 - 1 \mu\text{m}$  with a mean value about 400 nm. The unexfoliated part of the mixtures is used to prepare reference bulk samples.

The final dispersions are inspected by UV-Vis spectroscopy (see Fig. S1a in ESI), giving extinction spectra which are in agreement with literature results<sup>31,57</sup>.

### 2.2 Optical trapping and flake metrology of hexagonal boron nitride

*Raman spectroscopy of trapped flakes.* The coupling of an optical tweezers setup to a monochromator allows the spectroscopy of the trapped objects<sup>35,48</sup> directly in liquid environment. For this reason, Raman and photoluminescence tweezers are very appealing applications especially with regards to the study of biological samples as they may avoid the complications connected to the immobilization on a substrate. Moreover, spectroscopic methods are potentially extremely useful in the study of inorganic micro- and nanoparticles such as upconverting nanoparticles<sup>53</sup>, single-walled carbon nanotubes<sup>32,61</sup> (SWNTs), and graphene flakes<sup>33</sup>. For example when aiming at sorting on the basis of their spectroscopic characteristics, SWNTs may be dispersed in aqueous environment with the aid of surfactants<sup>7</sup>. Their Raman spectra, however, must be recorded on drop-cast samples, and re-aggregation phenomena cannot be avoided. A similar problem must be faced for graphene obtained by liquid-phase exfoliation<sup>33</sup>. In this case, Raman tweezers may help in the study of the yield in graphene monolayers of the exfoliation process<sup>35</sup>, as it is known that the Raman spectrum of monolayer graphene has a well defined peak at a Raman shift of approximately  $\Delta_0 = 2700 \text{ cm}^{-1}$ , the shape of which is sensitive to the number of layers<sup>17</sup>.

The first order Raman spectrum of highly oriented hBN crystals is characterized by two modes at Raman shifts  $\Delta_0 = 51.8 \text{ cm}^{-1}$  and at  $\Delta_0 = 1366.2 \text{ cm}^{-1}$  due to the  $E_{2g}$  symmetry vibrations<sup>40,51</sup>. The low energy mode is due to the sliding motion of adjacent planes, while the high energy mode is due to the in-plane atomic vibrations of boron and nitrogen atoms<sup>40,51</sup>. In the case of flakes

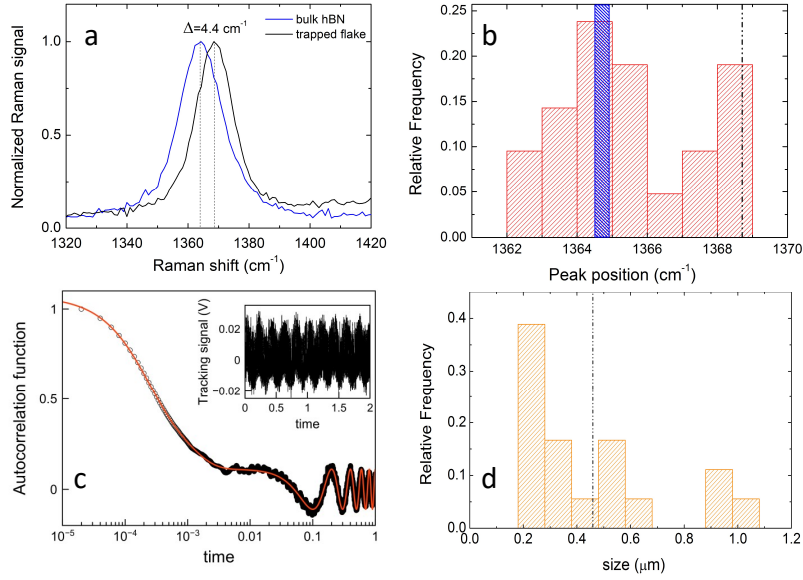


Figure 2: Spectroscopy, trapping and metrology of hBN flakes. (a) Comparison between the Raman spectra of bulk hBN (blue curve) and trapped hBN monolayer (black curve). The blue shift  $\Delta$  of the Raman peak of the monolayer with respect to the bulk value is also indicated. The exciting wavelength was  $\lambda=780$  nm. (b) Histogram of the Raman peak position of the trapped hBN flakes. The Raman peak positions  $\Delta_0 = 1364.7$   $\text{cm}^{-1}$  and  $\Delta_0 = 1368.6$   $\text{cm}^{-1}$  due to the bulk and the monolayer, respectively, are also indicated (blue bar and black dashed line). (c) Transverse signal autocorrelation function (black points) and its fit (red curve) with a double exponential decay plus a sinusoidal oscillation at  $\omega_{stage}$ . (d) Distribution of hBN flake size. The mean flake diameter  $d$  (dash-dot line) is approximately 460 nm. Bin size 100 nm, smallest diameter 180 nm.

obtained by micromechanical cleavage, monolayer hBN shows a blue shift of up to  $\Delta = 4$   $\text{cm}^{-1}$  of the high-energy Raman peak of the crystal, while bilayer samples, on the contrary, show a  $\Delta = 1 - 2$   $\text{cm}^{-1}$  red shift<sup>20</sup>.

In our measurements, a tightly focused (by an NA=1.3 objective) laser beam (7 mW at the sample) with 780 nm wavelength has been used to both trap and excite the Raman scattering of the hBN flakes. Several flakes have been trapped, and their Raman spectra recorded. Each spectrum (see Figure 2a) has been fitted with a single Lorentzian peak plus a linear background. We obtained a distribution of the hBN peak Raman shifts (Figure 2 b) that is compatible<sup>20</sup> with the presence, in solution, of mono- (blue shift of the hBN peak between 2 and 4  $\text{cm}^{-1}$ ) and bilayer flakes (approximately 2  $\text{cm}^{-1}$  red shift of the hBN peak). The data have been compared with the value registered, in the same experimental configuration, on a bulk hBN sample, obtained by drop-casting the sediment residue after the centrifugation of the exfoliated hBN aqueous solution.

*Photonic force microscopy and flake metrology.* In an optical tweezers, optical forces on the trapped particle due to the interaction with the laser beam are measured by studying the Brownian motion of the particle in the confining optical potential, which for small displacements from equilibrium can be considered harmonic<sup>25</sup>. Here we first discuss the simple case of an optically trapped spherical particle and then we generalize the calibration protocol to the non-spherical case of the hBN flakes.

In the overdamped (inertialess) regime, the Langevin equation for a spherical particle reduces to<sup>47</sup>:

$$\frac{dx_i}{dt} = -\frac{k_i}{\gamma}x_i(t) + \xi_i(t), \quad (1)$$

where  $k_i$  are the trap spring constants in the directions  $x_i$ ,  $\gamma$  is the friction coefficient and  $\xi_i(t)$  a random displacement that is the consequence of Brownian motion<sup>25</sup>.

From tracking of the particle position fluctuations in the trap we obtain the optical trap stiffnesses,  $k_i$  and the conversion factors,  $\beta_i$ , between experimental units of the tracking signal, in volts, and physical distance, in  $\mu\text{m}$  (see ESI). Among the various approaches<sup>25</sup>, here we use the method of the particle position autocorrelation functions (ACFs), which highlights the complex dynamics of non-spherical particles in the trap<sup>24,33,34,38</sup>. The ACF of position fluctuations for a spherical particle in a harmonic potential follows an exponential decay<sup>25</sup>:

$$C_{ii}(\tau) = \langle x_i(t)x_i(t+\tau) \rangle = C_{ii}(0)e^{-\omega_i\tau} = \frac{k_B T}{k_i}e^{-\omega_i\tau} \quad (2)$$

where  $\omega_i = k_i/\gamma$  is the ACF relaxation frequency and the amplitude  $C_{ii}(0)$  is obtained from energy equipartition<sup>25</sup>. In our experiments

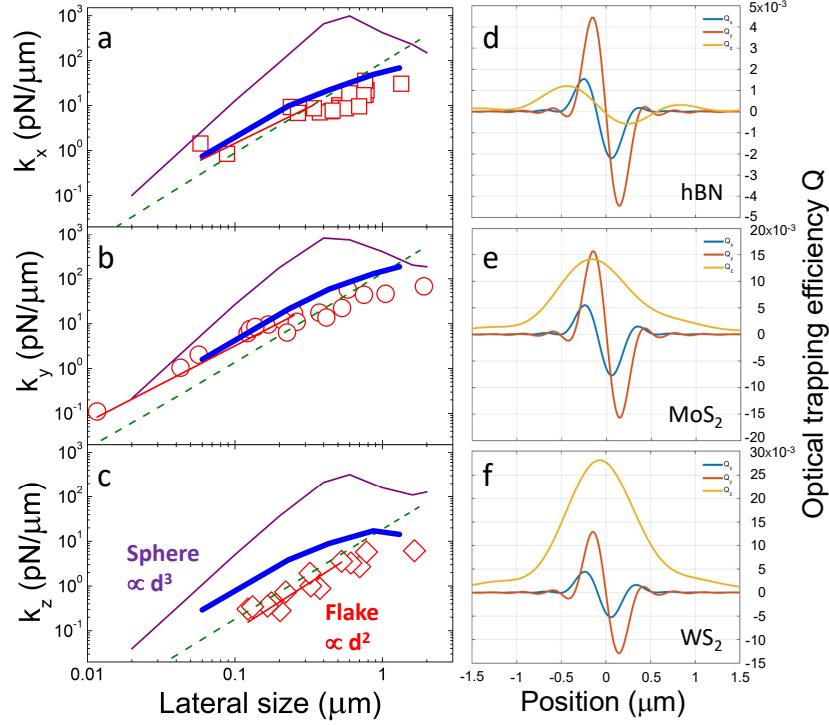


Figure 3: (a-c) Optical trap force constants  $k_x$  (red squares),  $k_y$  (red circles) and  $k_z$  (red diamonds) measured for trapped hBN flakes as a function of their lateral size determined from the autocorrelation analysis (note the log-log scale). Optical force measurements are obtained at 830 nm with 26 mW power at the sample. Red lines are a power law fit to the small size data consistent a size scaling of  $d^2$ . Purple lines are Mie theory calculations for a sphere, following a  $d^3$  scaling for small size. The dashed green lines represent the force constant estimates based on a simple dipole approximation (see ESI). Blue thick lines are T-matrix calculations for a planar cluster model of the hBN flake oriented in the  $xz$  plane because of optical torque. The agreement between experiments and T-matrix theory is excellent with no free parameters. (d-f) T-matrix calculations (830 nm, NA=1.3) of optical force efficiencies,  $Q_x$  (light blue),  $Q_y$  (red), and  $Q_z$  (yellow) for 0.9  $\mu\text{m}$  planar clusters of hBN (d), MoS<sub>2</sub> (e), and WS<sub>2</sub> (f). Note how  $Q_z$  has no zero for the case of MoS<sub>2</sub> and WS<sub>2</sub>, hence trapping is not possible because of the strong absorption of these materials in the near-infrared.

the particle position is tracked via back focal plane interferometry<sup>19</sup>, and thus the detector used to track the particle displacements records voltage signals that are proportional to particle displacements  $V_i(t) = \beta_i x_i(t)$ . We must therefore calibrate the trap and the detector system in order to find the voltage-length conversion factor  $\beta_i$ .

Since the ACF of the tracking signal fluctuations is related to that of the position fluctuations as:

$$C_{ii}^V(\tau) = \beta_i^2 C_{ii}(\tau) = \beta_i^2 \frac{k_B T}{k_i} e^{-\omega_i \tau}, \quad (3)$$

then from the fit of the voltage ACFs we obtain both the trap spring constant  $k_i$  and the voltage-length conversion factor  $\beta_i$ . When the hydrodynamic radius, that for spherical particles generally coincides with the physical radius,  $R$  is known, the friction coefficient  $\gamma = 6\pi\eta R$ , where  $\eta$  is the viscosity of the suspending medium<sup>47</sup>, can be easily calculated and a full calibration of optical forces is achieved by the ACF analysis. However, when particle radius is not known, it is still possible to calibrate the trap and to obtain the estimation of the size of the trapped particle by applying a deterministic motion to the particle<sup>12,62</sup>. Here, we apply a controlled sinusoidal oscillation to the microscope stage:

$$x(t) = A_{\text{stage}} \sin(\omega_{\text{stage}} t) \quad (4)$$

where  $A_{\text{stage}}$  is the oscillation amplitude and  $\omega_{\text{stage}}$  is the oscillation angular frequency. The trapped particle will thus be subjected to a similarly oscillating drag force

$$F_{\text{drag}} = -\gamma v_{\text{stage}} = -\gamma \omega_{\text{stage}} A_{\text{stage}} \cos(\omega_{\text{stage}} t), \quad (5)$$

and the tracking signal ACF will be:

$$C_{ii}^V(\tau) = A e^{-\omega_i \tau} + \frac{a_V^2}{2} \cos(\omega_{\text{stage}} \tau) = \beta_i^2 \frac{k_B T}{k_i} e^{-\omega_i \tau} + \frac{a_V^2}{2} \cos(\omega_{\text{stage}} \tau). \quad (6)$$

Here  $a_V$  is the amplitude of the oscillatory part of the tracking signal. In this case, the fit of the ACFs gives both the trap spring constants  $k_i$  and the calibration factors  $\beta_i$ . Additionally, the fit of the amplitude of the cosinusoidal oscillations provides a measure of the drag coefficients, from which it is possible to estimate the particle size (see ESI for details).

When the trapped particle is not spherical simply using the hydrodynamic radius does not give the correct description of the particle dynamics in the trap. In fact, non-spherical particles are oriented in the trap by the optical torque<sup>8,9</sup> and different drag coefficients must be considered to correctly model the Brownian dynamics along the trap axes<sup>24,33,34,38</sup>. This is particularly important when dealing with high aspect ratio nanoparticles such as hBN flakes. Moreover, the anisotropic hydrodynamics and the possibility of particle orientational fluctuations must be considered. In this case the ACFs may show a double-exponential decay, since the tracking signal contains contributions from both translational and rotational motion on different timescales, which are fitted to obtain both force and torque constants<sup>24,33,34,38</sup>. Here we model our trapped hBN particles as extremely thin disks (of diameter  $d$ ) parallel to the  $xz$  plane (where the axes are defined by the beam polarization,  $x$ , and the beam propagation,  $z$ , directions), and so we have to consider the drag coefficient  $\gamma_{\perp} = \frac{16}{3}\eta d$  for particle displacements in the  $x$  and  $z$  directions (displacements perpendicular to the symmetry axis of the flake), and the drag coefficient  $\gamma_{\parallel} = 8\eta d$  for displacements in the  $y$  direction<sup>33</sup>. Thus, in our experiments we measure these different drag coefficients and from each individual measurement we obtain an estimate of the trapped particle lateral size,  $d$ .

We oscillated the microscope stage in the  $x$ ,  $y$  and  $z$  directions at  $\omega_{\text{stage}} = 2\pi \times 5$  Hz and different amplitudes, depending on the strength of the optical trap. We measured the temperature of the sample chamber with a PT100 sensor to estimate the water viscosity  $\eta$ . We tracked the particle fluctuations using back focal plane interferometry, and calculated the corresponding ACFs. In Figure 2c a transverse signal autocorrelation function (black points) and its fit (red curve) with a double exponential decay plus a cosinusoidal oscillation at 5 Hz is shown. In this case the double exponential is necessary due to the signal contributions from orientational fluctuations of the flake. The fits of ACFs for each measurement were used to obtain the decay constants, the calibration parameters and the drag coefficients. Finally, the hBN flake lateral size,  $d$ , and optical trap spring constants,  $k_i$ , were obtained for each trapped flake. The resulting distribution of hBN flake size is shown in Fig. 2d. We estimated that the mean flake diameter is approximately 460 nm (dash-dot line) in good agreement with the value of 400 nm as estimated from TEM analysis of equivalent exfoliated samples in the literature<sup>31,57</sup> (see also Sec. 2.1).

In order to understand the optical force size-scaling for the hBN bi-dimensional system in Fig. 3(a-c) the trap spring constants  $k_x$  (red squares),  $k_y$  (red circles) and  $k_z$  (red diamonds) measured for each trapped hBN flake are shown as a function of their measured lateral size  $d$ . The experimental data are compared with: i) calculations of the trap spring constants based on the dipole approximation<sup>25</sup> (dashed green lines) for a flat spheroid<sup>5</sup> (see ESI for details), ii) T-matrix calculations<sup>8,9</sup> (thick blue lines) for a thin (10 nm) planar cluster with increasing lateral size (see Methods and ESI). To contrast the behaviour of the bi-dimensional system we also show (purple lines) the results of Mie theory for spheres with the same optical properties of hBN. At small flake size (smaller than the beam waist of about 300 nm), a scaling behaviour of the spring constants is observed. In fact, by fitting the data for small size with a power law (red lines in Fig. 3(a-c)),  $k_i \propto d^{\alpha}$ , we obtain  $\alpha \approx 1.7$  in the transverse ( $k_x, k_y$ ) direction and  $\alpha \approx 2.1$  for the axial ( $k_z$ ) one

with an uncertainty of about 20%. This is consistent with the quadratic,  $k_i \propto d^2$ , behaviour expected from dipole approximation results related to the quadratic increase of the real part of the polarizability for a small flat spheroid (see ESI). In contrast, a spherical particle (purple lines) at small size follows the well known volumetric behaviour<sup>25</sup>. However, when the flake size becomes comparable with the beam waist, optical forces tend to constant values, due to the saturation of the beam-particle interaction region. In this case,  $k_i$  changes its dependence with flake size, passing from an initial flattening to a progressive reduction at increasing  $d$ . We check this change of optical force behaviour at large flake size by an accurate modeling of optical trapping, for our experimental parameters (NA=1.3, 830 nm,  $P = 26$  mW), by using light scattering theory in the T-matrix approach<sup>54,55</sup> for a planar cluster model of the hBN flake oriented in the  $xz$  plane by the optical torque (thick blue lines in Fig. 3(a-c)). The agreement between experiments and T-matrix theory is excellent with no free parameters. The small discrepancy between the axial ( $k_z$ ) experimental points with respect to T-matrix calculations is related to the unavoidable aberration of the oil-immersion objective used in the experiments that weakens the trap along the beam propagation ( $z$ ) direction<sup>25</sup>.

### 2.3 Optical positioning of MoS<sub>2</sub> and WS<sub>2</sub>

Optical pushing of particles becomes possible when the gradient force is not able to overcome the scattering force. MoS<sub>2</sub> and WS<sub>2</sub> have larger extinction coefficients than hBN<sup>1,13,20,68</sup>, which justifies the fact that in our experimental conditions, and at the wavelengths used, we do not trap MoS<sub>2</sub> and WS<sub>2</sub> flakes in three dimensions. These observations are supported by T-matrix calculations (see Methods and ESI) of optical force efficiencies,  $Q_i = cF_i/n_mP$  ( $i = x, y, z$ ), for planar clusters shown in Fig. 3(d-f). Optical trapping occurs when  $Q_i$  vanish with a negative derivative<sup>9</sup>. A planar cluster of hBN (Fig. 3(d)) shows optical trapping in 3-D because the optical force efficiencies vanish in  $x, y, z$ . In contrast, a cluster with the same size but optical properties of MoS<sub>2</sub> (Fig. 3(e)) or WS<sub>2</sub> (Fig. 3(f)) shows optical trapping only in the transverse directions ( $x, y$ ), while it never shows a vanishing value of  $Q_z$  because of the strong absorption of these materials in the near-infrared resulting in a large increase of radiation pressure (See also ESI for a comparison using simple analytical dipole approximation results).

However, this large radiation pressure help us with the positioning of these particles onto flat surfaces. As shown in Video 1, we observe the 2D confinement of these flakes when the laser beam is focused near the microscope slide surface. In particular, we observe that MoS<sub>2</sub> and WS<sub>2</sub> flakes are pushed away from the laser focus when the beam is focused from the coverslip inside the sample chamber, until we reach the opposite surface. Here, the flakes are pushed towards the surface and cannot escape from the trap, since the transverse gradient forces confine them in the laser spot. However, when the laser is off, the particles are free to move and disperse in the medium. At higher power, the flakes are temporarily stuck to the surface, but the aggregate is unstable (see Supplementary Video 2). Furthermore, thermal effects such as the creation of bubbles in the host medium are observed, due to material absorption.

*Positioning with proteins.* Recently<sup>16</sup>, optical aggregation of gold (Au) nanorods has been achieved to realize SERS sensors for proteins directly in aqueous environment. Proteins in solution link to the Au nanorods, forming protein-nanorods complexes that under optical pushing are guided towards the substrate and create macroscopic aggregates. Here, we add a buffered Bovine Serum Albumin (BSA) aqueous solution to our MoS<sub>2</sub> and WS<sub>2</sub> dispersion, to help adhesion of the 2D flakes to the substrate and achieve controlled patterning of a substrate.

In Fig. 1 (c,d,e) the formation of an aggregate of WS<sub>2</sub>+BSA on a standard, untreated, glass microscope slide obtained by optically pushing from aqueous solution with a Gaussian beam is shown. The formed WS<sub>2</sub>+BSA aggregate is stably adhered to the surface. Moreover, patterning of the substrate is possible by shaping the pushing beam intensity profile. In Fig.1 (f,g,h) and Supplementary Video 3 the formation of an annular pattern on the microscope slide is obtained by pushing the MoS<sub>2</sub>+BSA solution with a high-order (topological charge  $l=30$ ) ring-shaped Laguerre-Gauss (LG) beam<sup>25,45</sup> generated by a spatial light modulator (see Methods). LG beams are frequently used in optical tweezers experiments, both for the transfer of orbital angular momentum leading to controlled rotations<sup>45,56</sup>, and for the optical trapping of objects that are repelled from the high intensity part of the laser beam due to their optical properties<sup>37</sup>. Here, use of the LG beam acts as a proof of principle that more complex patterning beyond the clusters formed by a simple Gaussian beam is possible with appropriate beam shaping.

*Spectroscopy and aggregate temporal evolution.* Raman spectroscopy of MoS<sub>2</sub> and WS<sub>2</sub> has been used in recent studies as a tool to distinguish mono- and few-layer flakes from bulk crystals<sup>3,13,22,26,28</sup>. In fact, it has been observed that the first order Raman features due to the  $E_{2g}^1$  and  $A_{1g}$  modes at approximately 382 and 408 cm<sup>-1</sup> in MoS<sub>2</sub><sup>28,66</sup>, and at approximately 355.5 cm<sup>-1</sup> and 420.5 cm<sup>-1</sup> in WS<sub>2</sub><sup>22</sup> approach each other in monolayer flakes, and move to the frequencies of the bulk when more than six layers are present in the flake. Moreover, in the case of a Raman excitation energy near to an absorption transition of the material, a resonant scattering process occurs, giving rise to a spectrum with several second order (*i.e.*, involving two phonons) features<sup>15,28</sup>.

We have studied the aggregation process of our 2D exfoliated materials by following the temporal evolution of their Raman spectra. We used an exciting wavelength ( $\lambda = 638$  nm) that gives resonant Raman scattering in both materials. Each Raman spectrum has been recorded within ten seconds of laser pushing (see Methods). The spectra registered on MoS<sub>2</sub> aggregates at increasing deposition time are shown in Figure 4b. Upon fitting, we found  $E_{2g}^1$  peaks at  $\Delta_0 = 383 - 384$ cm<sup>-1</sup>, and  $A_{1g}$  peaks between  $\Delta_0 = 406$  cm<sup>-1</sup> and  $\Delta_0 = 408$  cm<sup>-1</sup>. These values are consistent with those observed in few layer flakes<sup>26</sup> obtained by mechanical

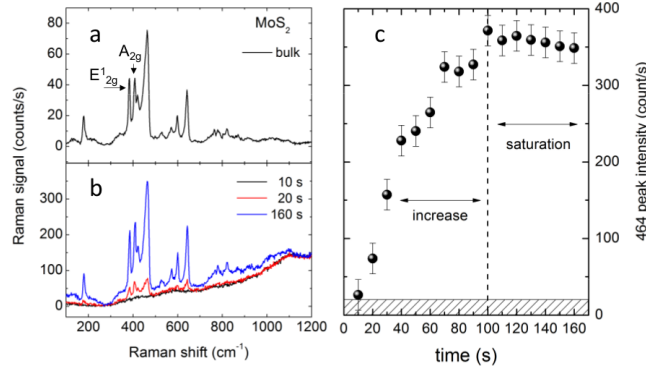


Figure 4: Optical force aggregation of MoS<sub>2</sub>. Raman spectra obtained on bulk MoS<sub>2</sub> (a) and under laser pushing of exfoliated MoS<sub>2</sub> at 638 nm (b). In (a), a long-working distance (LWD)  $\times 50$  objective (NA=0.5) has been used, while in (b) a  $\times 100$  oil immersion objective (NA=1.3) has been used. (c) Time evolution of 2LA(M) peak at  $\Delta_0 \approx 464 \text{ cm}^{-1}$  shown in (b). A clear increase of the peak signal is observed in the first 100 s of the pushing process, followed by its stabilization and saturation, due to the complete filling of the sampling volume of laser beam.

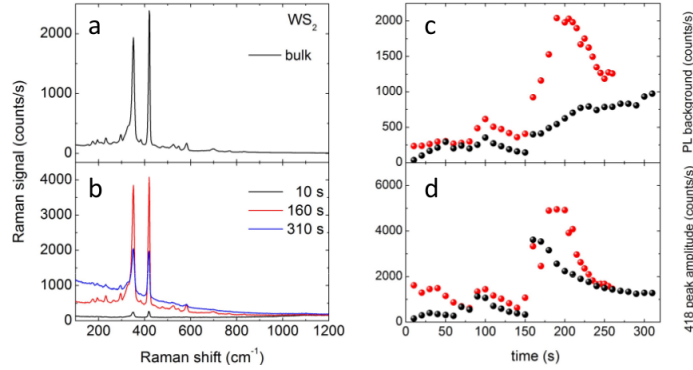


Figure 5: Optical force aggregation of WS<sub>2</sub>. On the left, Raman spectra obtained on bulk WS<sub>2</sub> (a) and under laser pushing of exfoliated WS<sub>2</sub> (b). For the spectrum of the bulk, the  $\times 50$  LWD objective has been used. On the right, the time evolution of the photoluminescence background (c) and of the  $\Delta_0 \approx 417 \text{ cm}^{-1}$  Raman peak (d) of WS<sub>2</sub> for two different pushing powers (black dots,  $\sim 5 \text{ mW}$ ; red dots,  $\sim 17 \text{ mW}$ ) are shown. In these plots, the error bars are smaller than the data marker size. Exciting wavelength  $\lambda = 638 \text{ nm}$ .

exfoliation, and, as also observed in samples obtained by LPE<sup>57</sup>, they are close to the values ( $\sim 383$  and  $\sim 407 \text{ cm}^{-1}$ ) obtained on the reference sample (Figure 4a), which has been prepared with the residue at the bottom of the centrifugation cell.

The temporal evolution of the aggregate has been studied by focusing on the most prominent feature in the resonant Raman spectrum, *i.e.*, the peak at approximately  $\Delta_0 = 464 \text{ cm}^{-1}$  due to an overtone of a longitudinal acoustic (LA) phonon<sup>66</sup> at the M point ( $232 \text{ cm}^{-1}$ ). The spectrum obtained after the first ten seconds of pushing is featureless, but after twenty seconds (Figure 4b) a small Raman signal is observed that is consistent with the results obtained in few-layer MoS<sub>2</sub> at the excitation wavelength  $\lambda = 633 \text{ nm}$ <sup>28</sup>. The signal amplitude gradually increases, indicating the increase of the aggregate size. When the formed aggregate completely fills the sampling volume of the laser beam, the Raman signal saturates. In Figure 4c, the time evolution of the 2LA(M) peak at  $464 \text{ cm}^{-1}$  clearly summarizes these results.

Note that we cannot discriminate a single particle increase for consecutive Raman spectra. This is because the large range in lateral flake size<sup>31,57</sup> ( $0.1 - 1 \mu\text{m}$ ) in the dispersion is such that a single flake Raman signal can have a large variation in intensity and, in our ten seconds acquisition time, we cannot distinguish between the intensity of a single large flake or the signal from few small ones.

In the case of pushing with a non-resonant wavelength ( $\lambda = 785 \text{ nm}$ ), some differences between the spectra obtained on the exfoliated material and on the bulk can be observed (see ESI). All the features in the spectra of the pushed material can be explained on the basis of the phononic spectrum of MoS<sub>2</sub><sup>66</sup>. The great enhancement of the LA(M) peak at approximately  $234 \text{ cm}^{-1}$  with respect to the bulk could be explained by the presence of defects at the edges of our exfoliated flakes<sup>4</sup>, as is observed also in liquid exfoliated graphene flakes<sup>33</sup>. This could explain also the low amplitude of the  $E_{2g}^1$  and  $A_{1g}$  peaks observed in the spectra of exfoliated materials when compared with the corresponding values in bulk.

A similar spectroscopic study of the pushing and aggregation process in exfoliated WS<sub>2</sub> has been carried out. In Figure 5a and



b, the Raman spectra obtained at  $\lambda = 638$  nm exciting wavelength on bulk (Figure 5 a) and on a growing aggregate (Figure 5 b) are shown. All the Raman features can be explained on the basis of the phononic spectrum of the material. It is worth noting that at resonant Raman excitation a peak at approximately  $350\text{ cm}^{-1}$ , due to an overtone of a LA(M) phonon, becomes more prominent, nearly overshadowing the  $E_{2g}^1$  peak. Upon fitting, we cannot separate the contribution of these two peaks, that are convoluted. On the contrary, the  $A_{1g}$  peak is easily fitted, giving values  $\Delta_0 = 418 - 419\text{ cm}^{-1}$ , which are consistent<sup>3</sup> with the presence in solution of few-layer flakes. The spectra are overlapped to a broad background that can be associated with the low energy tail of a PL emission centered at 630 nm due to defects present at the edges of  $\text{WS}_2$  monolayers of small size ( $< 5\ \mu\text{m}$ )<sup>3,22</sup>. On the basis of these results, the dynamics of the aggregation process has been followed by focusing on this PL background (Figure 5c) and on the Raman peak at  $418\text{ cm}^{-1}$ . At increasing deposition time, an overall increase of both signals is observed, which is consistent with an average increase of the aggregate size. However, this process goes through a series of increasing-decreasing steps, that are more evident at higher laser power. This could be explained by supposing an annealing effect of the aggregate structure, which is interrupted when a new flake adds to the aggregate. Finally, it is worth noting that, because of its low concentration, the presence of BSA in solution does not alter the Raman spectra of the deposited materials.

### 3 Conclusions

In conclusion, in this work we demonstrate that optical forces are powerful tools for the manipulation, positioning and characterization of liquid exfoliated 2D nanoparticles directly in their environment. On one hand, optical trapping can be used for metrology of exfoliated hBN, to determine the size of few-layer flakes obtained in the deposition process. On the other hand, optical pushing can be used to pattern common substrates such as microscope slides with  $\text{MoS}_2$  and  $\text{WS}_2$ . Importantly, both techniques can be combined with spectroscopic tools for material characterization, such as quantifying the number of layers in the flake. This could be particularly useful for the controlled patterning of substrates with layered materials or to realize mixed Van der Waals structures with layered materials of different origin.

## 4 Methods

### 4.1 Liquid phase exfoliation of two-dimensional materials

The hBN,  $\text{MoS}_2$  and  $\text{WS}_2$  powders were purchased from Sigma Aldrich. In all cases, the starting material showed platelet shapes. The powders generally consist of flakes with lateral size of  $1\ \mu\text{m}$  in case of hBN and approximately  $2\ \mu\text{m}$  and  $6\ \mu\text{m}$  in  $\text{WS}_2$  and  $\text{MoS}_2$ , respectively. The initial size of the microplatelets is important to obtain a high quality final product<sup>13,57</sup>. The layered compounds are dispersed in sodium cholate/water solution ( $0.045\text{ mg/mL}$ ) at a concentration of  $0.15\text{ mg/mL}$  through horn ultrasonication (Branson Sonifier 250) for 30 minutes. To reduce solvent heating and, thus, sample degradation, the dispersion were submerged in an ice bath. The sonication process results in dark green dispersions for  $\text{MoS}_2$  and  $\text{WS}_2$  and milky white dispersions for hBN (Fig. 1a). The dispersions are then transferred to a glass pot ( $40\text{ mL}$ ) and allowed to decant overnight. Finally, the top part ( $20\text{ mL}$ ) of the dispersions is centrifuged at about  $1500\text{ rpm}$  (revolutions per minute) for 15 minutes so to increase the amount of few-layered flakes.

### 4.2 Optical and Raman tweezers

Our optical and Raman tweezers are based on an inverted microscope configuration. Optical trapping and metrology of hBN flakes have been carried out using an exciting beam with wavelength  $830\text{ nm}$  derived from a laser diode (Thorlabs DL8142-201). The laser beam, after the passage through an anamorphic prism pair, is expanded by a 1:4 telescope. The resulting beam overfills the back aperture of a high numerical aperture ( $\text{NA}=1.3$ ) oil immersion objective and is focused to a laser spot  $\sim 600\text{ nm}$  in diameter. The power at the sample is approximately  $26\text{ mW}$ . The sample chamber (volume  $80\ \mu\text{L}$ ) is realized with a cavity well microscope slide, covered by a No. 1.5 coverslip and sealed. The chamber is mounted on a nanopositioning system (Mad City Labs Nano-LP200) with a  $200\ \mu\text{m}$  range of motion on each  $x$ ,  $y$  and  $z$  direction, at  $0.4\text{ nm}$  resolution. A thermoresistive sensor (PT100) has been mounted on the chamber to monitor its temperature. Particle tracking and force sensing have been obtained through back focal plane interferometry<sup>19,47</sup>, where the interference pattern from the unscattered and scattered light by the trapped particle is collected onto a quadrant photodiode (QPD). For flake metrology, after trapping, a controlled sinusoidal oscillation at  $5\text{ Hz}$  is imposed on the stage for  $x$ ,  $y$  and  $z$  directions separately, and the tracking signals registered independently. Three measurements for each direction are carried out. Thus, the signal autocorrelation functions are calculated and fitted as outlined in the main text. In general, a single exponential decay plus a cosinusoidal oscillation is used for fitting the signal along  $z$ . For the signals along  $x$  and  $y$ , a double exponential decay plus an oscillation is used. We repeated this procedure on eighteen different flakes.

Raman tweezers experiments are carried out on a different setup. A beam from a diode laser (Thorlabs DL7140-201S) at  $780\text{ nm}$ , passing through an anamorphic prism pair, is enlarged by a 1:2 telescope and delivered by means of a notch filter (Semrock NF03-785E-25) to the back aperture of a high numerical aperture ( $\text{NA}=1.3$ ) oil immersion objective and used for both trapping and

excitation of the Raman response of the trapped flake. The laser power at the sample chamber is approximately 7 mW. The sample chamber is mounted on a piezostage (Physics Instruments, P-517.3 CL) with 1 nm resolution. The backscattered light passes through the notch filter, used for Rayleigh scattering removal, and is subsequently focused by a 50 mm focal length lens onto a Horiba Jobin-Yvon Triax 190 spectrometer (190 mm focal length) equipped with a 1200 lines/mm grating blazed at 650 nm. A high sensitivity CCD (Horiba Jobin-Yvon Synapse) is used for signal detection. A beam splitter is inserted in the optical path to reflect 50% of the scattered light toward a CCD camera (Thorlabs USB 2.0, DCU223M), allowing for visual inspection of the trapped particle. To evaluate the reference value of the  $E_{2g}$  Raman peak in bulk hBN for comparison with the Raman peaks from trapped flakes, a small amount of the highly concentrated hBN solution taken at the bottom of the centrifuge cell is put on a coverslip and spectra are registered by focusing the laser through the coverslip itself, in the same experimental configuration of trapping experiments. To avoid thermal shifts of the Raman peak, a laser power of approximately 0.7 mW is used.

### 4.3 Optical force positioning

Optical pushing and aggregation of MoS<sub>2</sub> and WS<sub>2</sub> flakes is performed in an experimental set-up using an inverted microscope (Zeiss Axiovert 40 CFL). A high numerical aperture oil immersion objective (NA=1.3) focuses the incoming laser beam at 785 nm on the inner surface of the sample cell (Figure 1 b). A CCD camera (Thorlabs DCC 1645C-HQ) is used to image the sample during the aggregation process. To create a circular pattern on the surface we used an LG beam which has a doughnut-shaped intensity distribution. The LG beam with  $l = 30$  topological charge used in Fig.1 f-h and in Video 3 is generated by a spatial light modulator (Hamamatsu LCOS-SLM X10468-02). This device is used as a diffractive optical element to modulate the phase of the incoming laser beam. To this aim, a computer-generated holographic mask is projected on the SLM plane<sup>25</sup>. By means of two lenses ( $f= 750$  mm and 300 mm), this plane is imaged onto the back focal plane of the objective. Thus, at the focal plane of the objective the Fourier transform of the SLM plane is obtained<sup>47</sup>.

### 4.4 Raman spectroscopy of positioned samples

Raman spectroscopy of the MoS<sub>2</sub> and WS<sub>2</sub> aggregation process by optical pushing is carried out by means of a Horiba Jobin-Yvon Xplora system at 638 and 785 nm. The sample chamber has been realized with microscope slide, a  $\sim 120 \mu\text{m}$  adhesive spacer and a No. 1.5 coverslip. A  $10^{-4}$  M Bovine Serum Albumin (BSA) in phosphate buffer solution (200 mM) has been added to the layered material solution. All the pushing measurements have been carried out by focusing the laser spot on the inner microscope slide surface. The flakes entering the laser beam are pushed toward the surface and adhere to the glass surface. During the aggregation process, single-shot Raman spectra are sequentially collected with an acquisition time of 10 s. By using a 1200 lines/mm grating, a single spectral window is enough to cover the range  $100\text{-}1200 \text{ cm}^{-1}$  at both the wavelengths used. Data shown in Figs. 4 b, c and 5 b have been obtained with 638 nm excitation wavelength and at approximately 4.7 mW laser power at the sample, corresponding to an estimated irradiance of about  $8 \times 10^{10} \text{ W/m}^2$  (calculated considering a diffraction limited spot). Aiming at a comparison, we used as reference the Raman spectra registered, at low laser power (0.35 mW), on samples obtained by drying a small amount of the unexfoliated fraction of the MoS<sub>2</sub> and WS<sub>2</sub> dispersions, taken at the bottom of the centrifuge tube.

### 4.5 T-matrix calculations

Optical forces on layered material flakes are calculated by solving the light scattering problem in the T-matrix formalism<sup>54,55</sup> for planar clusters (see also ESI). The incident fields are the tightly focused fields creating the optical tweezers with the same parameters of the optical trapping experiments. First, we calculate the incident focal fields for the high NA (1.3) objective lens by using the angular spectrum representation<sup>9</sup> in the absence of any particle. Thus, the radiation force and torque<sup>8</sup> exerted on the planar cluster flake within the focal region are calculated by integrating the time-averaged Maxwell stress tensor<sup>25</sup>,  $\bar{\mathbf{T}}_{\text{M}}$ , on a large sphere of radius  $r$  surrounding the particle<sup>8,9</sup>:

$$\mathbf{F}_{\text{rad}} = r^2 \oint_{\Omega} \bar{\mathbf{T}}_{\text{M}} \cdot \hat{\mathbf{r}} d\Omega, \quad (7)$$

$$\mathbf{T}_{\text{Rad}} = -r^3 \oint_{\Omega} (\bar{\mathbf{T}}_{\text{M}} \times \hat{\mathbf{r}}) \cdot \hat{\mathbf{r}} d\Omega, \quad (8)$$

where the integration is over the full solid angle. The radiation force and torque are then expressed in terms of incident and scattered fields that can be expanded, respectively, in vector spherical harmonics<sup>25</sup> regular at the origin (Bessel multipoles) or at infinity (Hankel multipoles). Thus, the T-matrix for the scattering process<sup>54,55</sup> is defined as the linear operator that links the scattered expansion amplitudes to the incident ones. Finally, optical force and torque components are obtained by projecting the radiation force and torque vectors on the different coordinate axes, *e. g.*,  $F_x = \mathbf{F}_{\text{rad}} \cdot \hat{\mathbf{x}}$  or  $T_z = \mathbf{T}_{\text{rad}} \cdot \hat{\mathbf{z}}$ , and calculating the corresponding numerical integral<sup>8,9</sup>. For the planar cluster model used for the case of layered materials, we exploit the T-matrix formulation of light scattering by a cluster of spheres<sup>54,55</sup> (see ESI) where the fields scattered by the spherical subunits composing the planar cluster are combined by means of the addition theorem of multipole fields through a translation matrix<sup>25</sup>.

## 5 Conflicts of interest

There are no conflicts to declare.

## 6 Acknowledgements

We acknowledge support from ‘Programma Operativo Nazionale Ricerca e Competitività’ 2007-2013, Project PAC02L3-00087 SOCIAL-NANO and Project PON03PE-00214-2 DELIAS, MPNS COST Action 1205 ‘Advances in Optofluidics: Integration of Optical Control and Photonics with Microfluidic’ and MP1302 ‘Nanospectroscopy’.

## References

- [1] S. Alfihed, M. Hossain, A. Alharbi, A. Alyamani, and F. H. Alharbi. PLD grown polycrystalline tungsten disulphide (WS<sub>2</sub>) films. *J. Mater.*, 2013:603648, 2013.
- [2] A. Ashkin, J. Dziedzic, J. Bjorkholm, and S. Chu. Observation of a single-beam gradient optical trap for dielectric particles. *Opt. Lett.*, 11:288, 1986.
- [3] A. Berkdemir, H. R. Gutiérrez, A. R. Botello-Méndez, N. Perea-López, A. L. Elías, C.-I. Chia, B. Wang, V. H. Crespi, F. López-Urías, J.-C. Charlier, et al. Identification of individual and few layers of WS<sub>2</sub> using Raman spectroscopy. *Sci. Rep.*, 3:1755, 2013.
- [4] É. Blanco, P. Afanasiev, G. Berhault, D. Uzio, and S. Loridant. Resonance raman spectroscopy as a probe of the crystallite size of MoS<sub>2</sub> nanoparticles. *C. R. Chim.*, 19(10):1310–1314, 2016.
- [5] C. F. Bohren and D. R. Huffman. *Absorption and scattering of light by small particles*. John Wiley & Sons, 1998.
- [6] F. Bonaccorso, L. Colombo, G. Yu, M. Stoller, V. Tozzini, A. C. Ferrari, R. S. Ruoff, and V. Pellegrini. Graphene, related two-dimensional crystals, and hybrid systems for energy conversion and storage. *Science*, 347(6217):1246501, 2015.
- [7] F. Bonaccorso, T. Hasan, P. Tan, C. Sciascia, G. Privitera, G. Di Marco, P. Gucciardi, and A. Ferrari. Density gradient ultracentrifugation of nanotubes: Interplay of bundling and surfactants encapsulation. *J. Phys. Chem. C*, 114(41):17267–17285, 2010.
- [8] F. Borghese, P. Denti, R. Saija, and M. A. Iatì. Radiation torque on nonspherical particles in the transition matrix formalism. *Optics Express*, 14:9508–9521, 2006.
- [9] F. Borghese, P. Denti, R. Saija, and M. A. Iatì. Optical trapping of nonspherical particles in the T-matrix formalism. *Opt. Express*, 15:11984–11998, 2007.
- [10] L. Britnell, R. Ribeiro, A. Eckmann, R. Jalil, B. Belle, A. Mishchenko, Y.-J. Kim, R. Gorbachev, T. Georgiou, S. Morozov, et al. Strong light-matter interactions in heterostructures of atomically thin films. *Science*, 340(6138):1311–1314, 2013.
- [11] O. Brzobohatý, M. Šiler, J. Trojek, L. Chvátal, V. Karásek, A. Paták, Z. Pokorná, F. Mika, and P. Zemánek. Three-dimensional optical trapping of a plasmonic nanoparticle using low numerical aperture optical tweezers. *Sci. Rep.*, 5:8106, 2015.
- [12] A. Buosciolo, G. Pesce, and A. Sasso. New calibration method for position detector for simultaneous measurements of force constants and local viscosity in optical tweezers. *Opt. Commun.*, 230(4):357–368, 2004.
- [13] J. N. Coleman, M. Lotya, A. O’Neill, S. D. Bergin, P. J. King, U. Khan, K. Young, A. Gaucher, S. De, R. J. Smith, et al. Two-dimensional nanosheets produced by liquid exfoliation of layered materials. *Science*, 331(6017):568–571, 2011.
- [14] M. G. Donato, S. Vasi, R. Sayed, P. H. Jones, F. Bonaccorso, A. C. Ferrari, P. G. Gucciardi, and O. M. Maragò. Optical trapping of nanotubes with cylindrical vector beams. *Opt. Lett.*, 37:3381–3383, 2012.
- [15] J.-H. Fan, P. Gao, A.-M. Zhang, B.-R. Zhu, H.-L. Zeng, X.-D. Cui, R. He, and Q.-M. Zhang. Resonance raman scattering in bulk 2H-MX<sub>2</sub> (M= Mo, W; X= S, Se) and monolayer MoS<sub>2</sub>. *J. Appl. Phys.*, 115(5):053527, 2014.
- [16] B. Fazio, C. D’Andrea, A. Foti, E. Messina, A. Irrera, M. G. Donato, V. Villari, N. Micali, O. M. Maragò, and P. G. Gucciardi. Sers detection of biomolecules at physiological ph via aggregation of gold nanorods mediated by optical forces and plasmonic heating. *Sci. Rep.*, 6:26952, 2016.

- [17] A. C. Ferrari, J. Meyer, V. Scardaci, C. Casiraghi, M. Lazzeri, F. Mauri, S. Piscanec, D. Jiang, K. Novoselov, S. Roth, et al. Raman spectrum of graphene and graphene layers. *Phys. Rev. Lett.*, 97(18):187401, 2006.
- [18] A. K. Geim and I. V. Grigorieva. Van der waals heterostructures. *Nature*, 499(7459):419–425, 2013.
- [19] F. Gittes and C. F. Schmidt. Interference model for back-focal-plane displacement detection in optical tweezers. *Opt. Lett.*, 23(1):7–9, 1998.
- [20] R. V. Gorbachev, I. Riaz, R. R. Nair, R. Jalil, L. Britnell, B. D. Belle, E. W. Hill, K. S. Novoselov, K. Watanabe, T. Taniguchi, et al. Hunting for monolayer boron nitride: optical and raman signatures. *Small*, 7(4):465–468, 2011.
- [21] M. J. Guffey and N. F. Scherer. All-optical patterning of au nanoparticles on surfaces using optical traps. *Nano Lett.*, 10(11):4302–4308, 2010.
- [22] H. R. Gutiérrez, N. Perea-López, A. L. Elías, A. Berkdemir, B. Wang, R. Lv, F. López-Urías, V. H. Crespi, H. Terrones, and M. Terrones. Extraordinary room-temperature photoluminescence in triangular WS<sub>2</sub> monolayers. *Nano Lett.*, 13(8):3447–3454, 2012.
- [23] Y. Hernandez, V. Nicolosi, M. Lotya, F. M. Blighe, Z. Sun, S. De, I. McGovern, B. Holland, M. Byrne, Y. K. Gun'Ko, et al. High-yield production of graphene by liquid-phase exfoliation of graphite. *Nat. Nanotechnol.*, 3(9):563–568, 2008.
- [24] A. Irrera, P. Artoni, R. Saija, P. G. Gucciardi, M. A. Iatì, F. Borghese, P. Denti, F. Iacona, F. Priolo, and O. M. Maragò. Size-scaling in optical trapping of silicon nanowires. *Nano Lett.*, 11:4879–4884, 2011.
- [25] P. H. Jones, O. M. Maragò, and G. Volpe. *Optical tweezers: Principles and applications*. Cambridge University Press, Cambridge, 2015.
- [26] C. Lee, H. Yan, L. E. Brus, T. F. Heinz, J. Hone, and S. Ryu. Anomalous lattice vibrations of single-and few-layer MoS<sub>2</sub>. *ACS Nano*, 4(5):2695–2700, 2010.
- [27] A. Lehmuskero, P. Johansson, H. Rubinsztein-Dunlop, L. Tong, and M. Kall. Laser trapping of colloidal metal nanoparticles. *ACS Nano*, 9(4):3453–3469, 2015.
- [28] H. Li, Q. Zhang, C. C. R. Yap, B. K. Tay, T. H. T. Edwin, A. Olivier, and D. Baillargeat. From bulk to monolayer MoS<sub>2</sub>: evolution of raman scattering. *Adv. Funct. Mater.*, 22(7):1385–1390, 2012.
- [29] L. H. Li and Y. Chen. Atomically thin boron nitride: unique properties and applications. *Adv. Funct. Mater.*, 26(16):2594–2608, 2016.
- [30] X. Ling, W. Fang, Y.-H. Lee, P. T. Araujo, X. Zhang, J. F. Rodriguez-Nieva, Y. Lin, J. Zhang, J. Kong, and M. S. Dresselhaus. Raman enhancement effect on two-dimensional layered materials: graphene, h-BN and MoS<sub>2</sub>. *Nano Lett.*, 14(6):3033–3040, 2014.
- [31] M. Lotya, A. Rakovich, J. F. Donegan, and J. N. Coleman. Measuring the lateral size of liquid-exfoliated nanosheets with dynamic light scattering. *Nanotechnology*, 24(26):265703, 2013.
- [32] O. Maragò, P. Gucciardi, and P. Jones. Photonic force microscopy: from femtonewton force sensing to ultra-sensitive spectroscopy. In *Scanning Probe Microscopy in Nanoscience and Nanotechnology*, pages 23–56. Springer, 2010.
- [33] O. M. Maragò, F. Bonaccorso, R. Saija, G. Privitera, P. G. Gucciardi, M. A. Iatì, G. Calogero, P. H. Jones, F. Borghese, P. Denti, V. Nicolosi, and A. C. Ferrari. Brownian motion of graphene. *ACS Nano*, 4:7515, 2010.
- [34] O. M. Maragò, P. H. Jones, F. Bonaccorso, V. Scardaci, P. G. Gucciardi, A. G. Rozhin, and A. C. Ferrari. Femtonewton force sensing with optically trapped nanotubes. *Nano Lett.*, 8:3211–3216, 2008.
- [35] O. M. Maragò, P. H. Jones, P. G. Gucciardi, G. Volpe, and A. C. Ferrari. Optical trapping and manipulation of nanostructures. *Nat. Nanotechnol.*, 8:807–819, 2013.
- [36] D. McManus, S. Vranic, F. Withers, V. Sanchez-Romaguera, M. Macucci, H. Yang, R. Sorrentino, K. Parvez, S.-K. Son, G. Iannaccone, K. Kostarelos, G. Fiori, and C. Casiraghi. Water-based and biocompatible 2d crystal inks for all-inkjet-printed heterostructures. *Nat. Nanotechnol.*, 12:343–350, 2017.
- [37] G. Memoli, C. R. Fury, K. O. Baxter, P. N. Gélât, and P. H. Jones. Acoustic force measurements on polymer-coated microbubbles in a microfluidic device. *The Journal of the Acoustical Society of America*, 141(5):3364–3378, 2017.

- [38] E. Messina, M. G. Donato, M. Zimbone, R. Saija, M. A. Iatì, L. Calcagno, M. E. Fragala, G. Compagnini, C. D'Andrea, A. Foti, P. G. Gucciardi, and O. M. Maragò. Optical trapping of silver nanoplatelets. *Opt. Express*, 23(7):8720–8730, 2015.
- [39] S. Nedev, A. S. Urban, A. A. Lutich, and J. Feldmann. Optical force stamping lithography. *Nano Lett.*, 11(11):5066–5070, 2011.
- [40] R. Nemanich, S. Solin, and R. M. Martin. Light scattering study of boron nitride microcrystals. *Phys. Rev. B*, 23(12):6348, 1981.
- [41] A. A. R. Neves, A. Camposeo, S. Pagliara, R. Saija, F. Borghese, P. Denti, M. A. Iatì, R. Cingolani, O. M. Maragò, and D. Pisignano. Rotational dynamics of optically trapped nanofibers. *Opt. Express*, 18(2):822–830, 2010.
- [42] K. Novoselov, D. Jiang, F. Schedin, T. Booth, V. Khotkevich, S. Morozov, and A. Geim. Two-dimensional atomic crystals. *Proc. Natl. Acad. Sci. USA*, 102(30):10451–10453, 2005.
- [43] K. S. Novoselov, V. Fal, L. Colombo, P. Gellert, M. Schwab, K. Kim, et al. A roadmap for graphene. *Nature*, 490(7419):192–200, 2012.
- [44] K. S. Novoselov, A. K. Geim, S. V. Morozov, D. Jiang, Y. Zhang, S. V. Dubonos, I. V. Grigorieva, and A. A. Firsov. Electric field effect in atomically thin carbon films. *Science*, 306(5696):666–669, 2004.
- [45] M. Padgett and R. Bowman. Tweezers with a twist. *Nat. Photon.*, 5:343–348, 2011.
- [46] P. J. Pauzauskie, A. Radenovic, E. Trepagnier, H. Shroff, P. Yang, and J. Liphardt. Optical trapping and integration of semiconductor nanowire assemblies in water. *Nat. Mater.*, 5(2):97, 2006.
- [47] G. Pesce, G. Volpe, O. M. Maragò, P. H. Jones, S. Gigan, A. Sasso, and G. Volpe. Step-by-step guide to the realization of advanced optical tweezers. *J. Opt. Soc. Am. B-Opt. Phys.*, 32(5):B84–B98, 2015.
- [48] D. V. Petrov. Raman spectroscopy of optically trapped particles. *J. Opt. A - Pure Appl. Op.*, 9:S139–S156, 2007.
- [49] A. Poddubny, I. Iorsh, P. Belov, and Y. Kivshar. Hyperbolic metamaterials. *Nat. Photon.*, 7(12):948–957, 2013.
- [50] P. J. Reece, W. J. Toe, F. Wang, S. Paiman, Q. Gao, H. H. Tan, and C. Jagadish. Characterization of semiconductor nanowires using optical tweezers. *Nano Lett.*, 11(6):2375–2381, 2011.
- [51] S. Reich, A. Ferrari, R. Arenal, A. Loiseau, I. Bello, and J. Robertson. Resonant raman scattering in cubic and hexagonal boron nitride. *Phys. Rev. B*, 71(20):205201, 2005.
- [52] H. Rodríguez-Rodríguez, P. Rodríguez Sevilla, E. Martín Rodríguez, D. H. Ortgies, M. Pedroni, A. Speghini, M. Bettinelli, D. Jaque, and P. Haro-González. Enhancing optical forces on fluorescent up-converting nanoparticles by surface charge tailoring. *Small*, 11(13):1555–1561, 2015.
- [53] P. Rodríguez-Sevilla, H. Rodríguez-Rodríguez, M. Pedroni, A. Speghini, M. Bettinelli, J. G. Solé, D. Jaque, and P. Haro-González. Assessing single upconverting nanoparticle luminescence by optical tweezers. *Nano Letters*, 15(8):5068–5074, 2015.
- [54] R. Saija, M. A. Iatì, F. Borghese, P. Denti, S. Aiello, and C. Cecchi-Pestellini. Beyond mie theory: the transition matrix approach in interstellar dust modeling. *The Astrophysical Journal*, 559(2):993–1004, 2001.
- [55] R. Saija, M. A. Iatì, P. Denti, F. Borghese, A. Giusto, and O. I. Sindoni. Efficient light-scattering calculations for aggregates of large spheres. *Applied Optics*, 42(15):2785–2793, 2003.
- [56] N. Simpson, L. Allen, and M. Padgett. Optical tweezers and optical spanners with laguerre–gaussian modes. *Journal of Modern Optics*, 43(12):2485–2491, 1996.
- [57] R. J. Smith, P. J. King, M. Lotya, C. Wirtz, U. Khan, S. De, A. O'Neill, G. S. Duesberg, J. C. Grunlan, G. Moriarty, et al. Large-scale exfoliation of inorganic layered compounds in aqueous surfactant solutions. *Adv. Mater.*, 23(34):3944–3948, 2011.
- [58] D. Spadaro, M. A. Iatì, M. G. Donato, P. G. Gucciardi, R. Saija, A. R. Cherlakola, S. Scaramuzza, V. Amendola, and O. M. Maragò. Scaling of optical forces on au–peg core–shell nanoparticles. *RSC Adv.*, 5(113):93139–93146, 2015.
- [59] D. Spadaro, M. A. Iatì, J. Perez-Pineiro, C. Vázquez-Vázquez, M. A. Correa-Duarte, M. G. Donato, P. G. Gucciardi, R. Saija, G. Strangi, and O. M. Marago. Optical trapping of plasmonic mesocapsules: Enhanced optical forces and SERS. *J. Phys. Chem. C*, pages 691–700, 2017.

- [60] S. E. S. Spesyvtseva and K. Dholakia. Trapping in a material world. *ACS Photon.*, 3(5):719–736, 2016.
- [61] S. E. S. Spesyvtseva, S. Shoji, and S. Kawata. Chirality-selective optical scattering force on single-walled carbon nanotubes. *Physical Review Applied*, 3(4):044003, 2015.
- [62] S. F. Tolić-Nørrelykke, E. Schäffer, J. Howard, F. S. Pavone, F. Jülicher, and H. Flyvbjerg. Calibration of optical tweezers with positional detection in the back focal plane. *Rev. Sci. Instrum.*, 77(10):103101, 2006.
- [63] F. Torrisi, T. Hasan, W. Wu, Z. Sun, A. Lombardo, T. S. Kulmala, G.-W. Hsieh, S. Jung, F. Bonaccorso, P. J. Paul, et al. Inkjet-printed graphene electronics. *ACS Nano*, 6(4):2992–3006, 2012.
- [64] A. S. Urban, S. Carretero-Palacios, A. A. Lutich, T. Lohmüller, J. Feldmann, and F. Jäckel. Optical trapping and manipulation of plasmonic nanoparticles: fundamentals, applications, and perspectives. *Nanoscale*, 6(9):4458–4474, 2014.
- [65] Q. H. Wang, K. Kalantar-Zadeh, A. Kis, J. N. Coleman, and M. S. Strano. Electronics and optoelectronics of two-dimensional transition metal dichalcogenides. *Nat. Nanotechnol.*, 7(11):699–712, 2012.
- [66] B. C. Windom, W. Sawyer, and D. W. Hahn. A raman spectroscopic study of MoS<sub>2</sub> and MoO<sub>3</sub>: applications to tribological systems. *Tribol. Lett.*, 42(3):301–310, 2011.
- [67] Z. Yan, J. E. Jureller, J. Sweet, M. J. Guffey, M. Pelton, and N. F. Scherer. Three-dimensional optical trapping and manipulation of single silver nanowires. *Nano Lett.*, 12(10):5155–5161, 2012.
- [68] C. Yim, M. O’Brien, N. McEvoy, S. Winters, I. Mirza, J. G. Lunney, and G. S. Duesberg. Investigation of the optical properties of MoS<sub>2</sub> thin films using spectroscopic ellipsometry. *Appl. Phys. Lett.*, 104(10):103114, 2014.